




Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil

Type of Document:	Product Definition and Specification Guidelines
Status of Document:	Final
Revision Number:	0.8
Revision Date:	15 May 2012
Original Date:	10 January 2011 For Public Posting
Document Reference Code:	IBI-STD-01

© International Biochar Initiative - May 2012

OWNERSHIP AND COPYRIGHT NOTICE

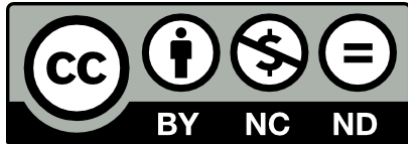

This work is licensed under the terms of the Creative Commons Attribution-NonCommercial-NoDerivs 3.0 Unported License attached in Appendix 7. Under this license,

You are free:

to **Share** — to copy, distribute and transmit the work

Under the following conditions:



Attribution — You must attribute the work to the International Biochar Initiative (IBI) (but not in any way that suggests that IBI endorses you or your use of the work).



Non-commercial — You may not use this work for commercial purposes.



No Derivative Works — You may not alter, transform, or build upon this work.

With the understanding that:

Waiver— Any of the above conditions can be waived if you get permission from the copyright holder.

Public Domain— Where the work or any of its elements is in the public domain under applicable law, that status is in no way affected by the license.

Other Rights— In no way are any of the following rights affected by the license:

- Your fair dealing or fair use rights, or other applicable copyright exceptions and limitations;
- The author's moral rights;
- Rights other persons may have either in the work itself or in how the work is used, such as publicity or privacy rights.

DISCLAIMER

The International Biochar Initiative (IBI) *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil* have been prepared with the intent of providing stakeholders and commercial entities with guidelines to identify certain qualities and characteristics of biochar materials according to relevant, reliable, and measurable characteristics. Producers who follow these *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil* do so voluntarily. In no way shall the IBI or its associates be responsible for the use or misuse of information and guidance provided in this document. Anyone making use of this document assumes all liability arising from such use.

IBI does not make, and hereby specifically disclaims, any representation, warranty, claim, or guarantee regarding biochar tested and characterized according to this document, including but not limited to any representation, warranty, claim, or guarantee relating to the safety or fitness of such biochar for a particular purpose. Independent professional judgment must be exercised when producing and using biochar and, IBI makes no representation or warranty as to the safety or quality of biochar tested and characterized according to this document. This document does not purport to address all of the safety concerns, if any, associated with the use of this document or the use or production of biochar tested and characterized according to this document. It is the responsibility of the user of this document, and the producers and users or consumers of biochar, to establish appropriate safety and health practices and determine the applicability of any national, state or provincial, and local regulatory limitations prior to use.

IBI does not make, and hereby specifically disclaims, any representation, warranty, claim, or guarantee regarding biochar that has not been tested and characterized according to this document, including but not limited to any representation, warranty, claim, or guarantee relating to the safety or fitness of such biochar for a particular purpose.

IBI is not a seller of biochar and does not make, and hereby specifically disclaims, any and all representations, endorsements, guarantees, and warranties, express or implied, regarding the use of this document or biochar tested and characterized according to this document, including, without limitation, the implied warranties of merchantability and fitness for a particular purpose, title and non-infringement of third-party rights. IBI advises consumers of biochar that, from IBI's perspective, all biochar tested and characterized according to this document is purchased as is and with all faults from the biochar producer.

IBI expressly disclaims any grant of apparent or actual authority from IBI to producers of biochar tested and characterized according to this document.

No portion of this document is intended for use as a sustainability or production process guideline. Further documentation and guidance is necessary to identify appropriate sustainability practices and/or safe and effective production processes.

The benefits of a given biochar material vary widely with the material and with crop, soil, and climate factors. This document makes no representations, claims, guarantees or warranties regarding the potential benefits of any given biochar material in any particular application.

The *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil* are intended to be revised and updated as the science and body of knowledge surrounding biochar continues to evolve. Please ensure that you are using the most up-to-date version found on the website of the International Biochar Initiative: <http://www.biochar-international.org>.

LIMITATION OF LIABILITY

Under no circumstances will IBI be liable for any loss or damage caused by your reliance on the information obtained from the *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil*. It is your responsibility to evaluate the accuracy, completeness, and usefulness of this document. In no event shall IBI be liable for any direct, indirect, punitive, incidental, special, or consequential damages arising out of or relating to the *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil*, whether based on warranty, contract, tort, strict liability, or any other legal theory. Because some jurisdictions do not allow the exclusion or limitation of liability for negligence, consequential, incidental, or other damages, in such jurisdictions IBI's liability is limited to the greatest extent permitted by law. If you are dissatisfied with any portion of the *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil*, your sole and exclusive remedy is to stop using the *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil*.

INDEMNITY

By using the *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil*, you hereby agree to defend and hold IBI harmless from and against any and all claims, actions, demands, liabilities, losses, settlements, costs and fees (including, without limitation, reasonable attorneys' fees and court costs), arising from or allegedly arising from your use or misuse of this document.

1 **Foreword**

2 The *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in*
3 *Soil* provide a standardized definition of biochar and biochar characteristics related to the use of
4 biochar as a soil amendment. They have been developed by the International Biochar Initiative
5 (IBI) in collaboration with a wide variety of industry and academic experts and through public
6 input on an international level. The *Standardized Product Definition and Product Testing*
7 *Guidelines for Biochar That Is Used in Soil* were created to encourage further development of
8 the biochar industry by providing standardized information regarding the characterization of
9 biochar materials to assist in achieving more consistent levels of product quality. In addition to
10 providing product definition and qualitative specification guidelines, this document has been
11 developed to assist biochar producers in providing consumers with consistent access to credible
12 information regarding qualitative and physicochemical properties of biochar.

13 The *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in*
14 *Soil* are designed to support an IBI certification program. Separately, the *Guidelines* are also
15 intended for use by various national and regional product standards bodies, and national and
16 regional biochar groups for their own local adaptation and use, and as a reference in regulatory
17 situations, as may be appropriate.

18 The *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in*
19 *Soil* were developed as a means of providing information and market certainty about the
20 attributes of biochars for use in soil applications. Ultimately, the use and promotion of these
21 *Guidelines* will build consumer and regulatory confidence about biochar, through the provision
22 of consistent and reliable information regarding biochar properties. Biochar can be made from a
23 variety of feedstocks, using a variety of different production processes, and can possess many
24 different attributes. The consistent reporting of biochar properties will ensure that pertinent
25 information about biochars for use in soil applications is systematically communicated,
26 regardless of feedstock type, production process, or final properties.

27 IBI developed the *Standardized Product Definition and Product Testing Guidelines for Biochar*
28 *That Is Used in Soil* in a transparent process open to public participation, review, and input.
29 Throughout the development process IBI relied upon the drafting, review, and guidance of
30 experts in the field, ensuring an efficient path from concept to final product, and addressing the
31 needs of a broad range of commercial biochar producers and end users. As the document was
32 developed, public input from the larger international biochar community was continuously
33 sought to provide a wider perspective on the use and functionality of this tool.

34 The design of the *Standardized Product Definition and Product Testing Guidelines for Biochar*
35 *That Is Used in Soil* follows current best practices and available science. As biochar science
36 continues to improve, the *Guidelines* will be updated in an iterative process in order to remain
37 current. Therefore these *Guidelines* and this document will be periodically revised through
38 further consultation with the international biochar community.

1 The *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in*
2 *Soil* document development process is based on the following guiding principles:

- 3 • Maintain congruence with best practice guidance for standards development such as
4 International Standards Organization (ISO), American Society for Testing and Materials
5 (ASTM), and Institute of Electrical and Electronics Engineers (IEEE);
- 6 • Strictly adhere to process, ensuring efficient and effective collaboration;
- 7 • Engage the knowledgeable and diverse stakeholder groups active in the biochar
8 industry;
- 9 • Organize independent working groups with broad stakeholder representation, and,
10 • Rely on IBI infrastructure and capacity for leadership and administration of the initiative.

11 The complete record of process documentation, including the list of working group members,
12 can be found on the IBI website at:

13 <http://www.biochar-international.org/characterizationstandard>.

1	Table of Contents	
2	OWNERSHIP AND COPYRIGHT NOTICE	2
3	Foreword	5
4	Table of Contents	7
5	1 Scope	8
6	2 Terms and Definitions	9
7	3 Biomass Feedstock Material and Biochar Production	9
8	3.1 General Feedstock Material Requirements	9
9	3.2 General Biochar Production and Material Handling Recommendations	9
10	4 Biochar Material Test Categories and Characteristics	10
11	4.1 Test Category A – Basic Utility Properties	11
12	4.2 Test Category B - Toxicant Reporting	13
13	4.3 Test Category C - Advanced Analysis and Soil Enhancement Properties	15
14	5 Product Labeling and Documentation	15
15	5.1 Labeling Instructions	16
16	5.2 Product Information Requirements	16
17	5.3 Conformity and Record Keeping	16
18	5.4 Chain of Custody	16
19	6 Testing Protocols	17
20	6.1 Laboratory Standards	17
21	6.2 Timing and Frequency of Testing	17
22	6.3 Category B Test Requirements for Unprocessed Feedstocks	18
23	7 References	19
24	Appendix 1 – Sample Biochar Label	22
25	Appendix 2 – Recommended General Sample Analysis Procedures and	
26	Protocols for Specific Tests	24
27	Appendix 3 – Toxicant Assessment and Determination of Thresholds	28
28	Appendix 4 – Determining a “Material Change” in Feedstock	30
29	Appendix 5 – The Use of H:C_{org} to Indicate C Stability	33
30	Appendix 6 – Glossary	36
31	Appendix 7 – Creative Commons License	42
32		

1 Scope

Issued by the International Biochar Initiative (IBI) and based on international consultation, this *Standardized Product Definition and Product Testing Guidelines for Biochar That Is Used in Soil* (hereinafter referred to as *Biochar Guidelines*) document is intended to establish a common definition for biochar, testing and measurement methods for selected physicochemical properties of biochar, and labelling guidelines for biochar materials.

Biochar is a solid material obtained from the thermochemical conversion of biomass in an oxygen-limited environment. Biochar can be used as a product itself or as an ingredient within a blended product, with a range of applications as an agent for soil improvement, improved resource use efficiency, remediation and/or protection against particular environmental pollution, and as an avenue for greenhouse gas (GHG) mitigation.

These *Biochar Guidelines* provide a standardized definition of biochar and biochar characteristics related to the use of biochar as a soil amendment. They will serve as the basis for an IBI certification program, and are intended for use and adaptation to local conditions and regulations by any nation or region. These *Biochar Guidelines* support not only baseline safety considerations but also the evolving understanding of the positive functions of biochar in soil. This document does not prescribe appropriate uses for biochar materials, nor provide guidelines on what biochar can or should be used for.

These *Biochar Guidelines* relate to the physicochemical properties of biochar only, and do not prescribe production methods or specific feedstocks, nor do they provide limits or terms for defining the sustainability and/or GHG mitigation potential of a biochar material, for a certification scheme or otherwise.

Different feedstock types, and hence differentiated testing requirements of biochar, are defined in this guidance document as means for the identification and classification of a range of biochar materials. This testing scheme is based upon increasing levels of physicochemical property reporting and not necessarily on increasing levels of biochar performance. The intended audiences for these *Biochar Guidelines* include commercial biochar producers, users, regulators, researchers and marketers, as well as the many national and regional biochar affiliates of the IBI. However, the commercial biochar producer is the entity most likely to apply the *Biochar Guidelines*, as a label (of differentiation) on its biochar material or product.

2 Terms and Definitions

A complete list of terms and definitions is found, along with a list of acronyms, in Appendix 6. A clear understanding of the defined terms is essential to the proper use of these *Biochar Guidelines*. Defined terms are indicated with a double underline in the text on the first instance of the use of that term.

3 Biomass Feedstock Material and Biochar Production

3.1 General Feedstock Material Requirements

The materials used as feedstocks for biochar production have direct impacts on the nature and quality of the resulting biochar. Although the focus of this document is on the biochar material, some restrictions have been applied to feedstock contents and quality. To qualify as biochar feedstock under these guidelines, the feedstock may be any combination of biomass and diluents, but may not contain more than 2% by dry weight of contaminants (following Brinton 2000). Any diluents that constitute 10% or more by dry weight of the feedstock material must be reported as a feedstock component on the product label.

Feedstocks are differentiated into two types: unprocessed feedstocks and processed feedstocks, with different requirements for sampling and analysis of potential toxic substances.

Suitable feedstocks include but are not limited to agriculture, food, and forestry residues, which may contain a minimal quantity of contaminants (see above) as part of the feedstock. Any feedstock that may have been grown on contaminated soils shall be considered to be a processed feedstock and must meet the toxicant assessment testing frequency requirements for processed feedstocks given in Section 6, *Testing Protocols*.

Municipal Solid Waste (MSW) containing hazardous materials or wastes may not be included as eligible feedstock under these guidelines. It is the manufacturer's responsibility to ensure that biochar feedstock materials are free of hazardous materials.

Note: Issues of feedstock sustainability are not addressed in this document.

3.2 General Biochar Production and Material Handling Recommendations

These *Biochar Guidelines* do not prescribe production and handling parameters for biochar, but do include recommendations for safe production processes. It is the responsibility of the biochar producer or manufacturer to create biochar in a safe manner. The IBI recommends that current best industry practices be followed throughout the manufacturing and handling process.

Local requirements and regulations for the operation of biochar production facilities should be followed. Where applicable, biochar production must comply with local and international

regulatory requirements and treaties that govern thermal processes, the production of volatile and particulate emissions, and the transport of goods. Relevant to local and international regulatory compliance, biochar producers should follow the two recommendations listed below:

- A biochar producer should provide a relevant material safety data sheet (MSDS) for the final output of its particular biochar production process. Brief outlines of MSDS document creation are available from numerous online sources, including [MSDS Search](#), the [Canadian Center for Occupational Health and Safety](#), and the [US Department of Labor Occupational Health and Safety Administration](#).
- Biochar should be tested to address the potential for self-heating and flammability during storage and transportation. Documentation of the results of this testing should be appended to the MSDS.

While the IBI may not require these practices as part of its definition and certification of biochar since they do not relate directly to product quality, they are important considerations in good business practices and responsible industrial production. The majority of nations provide detailed guidelines, expectations, and regulations governing the manufacturing sector and will have relevant information available to industrial operators.

4 Biochar Material Test Categories and Characteristics

As described in this section, biochar characteristics shall be assessed according to a defined set of test categories intended to provide increasing levels of physicochemical property reporting. A required set of tests to measure basic biochar characteristics that impact soil functions is supplemented with an optional test category for advanced analysis and soil enhancement properties. Toxicant assessment testing is required for all biochars. Increasing levels of physicochemical property testing and reporting do not correspond to increasing levels of biochar performance; rather, the categorization structure is designed to:

- provide a uniform presentation format by which a biochar user would be able to fairly compare and assess the reported properties of different biochar materials;
- provide a set of required tests for basic biochar utility and an optional set of additional tests for measuring advanced analysis and soil enhancement properties; and
- require toxicant reporting appropriate to the potential risks associated with both unprocessed and processed feedstocks. Increased testing frequency is required to attain quality assurance for processed feedstocks, which carry a higher potential risk of contamination.

Each test category was developed according to an assessment of the relevant parameters for biochar properties and safety, balanced against cost and accessibility.

These *Biochar Guidelines* identify three categories of tests for biochar materials:

Test Category A – Basic Utility Properties: ***Required for all biochars.*** This set of tests measures the most basic properties required to assess the utility of a biochar material for use in soil.

Test Category B – Toxicant Assessment: ***Required for all biochars.*** Biochars made from processed feedstocks must be tested more frequently than biochars made from unprocessed feedstocks, as defined in Section 6, *Testing Protocols*.

Test Category C – Advanced Analysis and Soil Enhancement Properties: Optional for all biochars. Biochar may be tested for advanced analysis and enhancement properties in addition to meeting test requirements for Category A. All tests in Test Category C are optional. Producers may report on none, one, some or all of the properties.

Further details on each of the test categories are provided in the following subsections.

4.1 Test Category A – Basic Utility Properties

All biochar must be tested for basic utility properties and meet the criteria specified under Test Category A, as shown in Table 1 below. Basic biochar characteristics include the physical properties of particle size and moisture, as well as the chemical properties of elemental proportions [Hydrogen (H), Carbon (C), and Nitrogen (N)], ash proportion, Electrical Conductivity (EC) and pH/liming ability. Organic carbon content (C_{org}) is used to assign the biochar material to a Class that is dependent on the percentage of C_{org} in the material. Carbon stability is indicated by the molar ratio of hydrogen to organic carbon. Lower values of this ratio are correlated with greater carbon stability. See Appendix 5, *The Use of $H:C_{org}$ to Indicate C Stability*, for more information on this analysis.

Table 1: Test Category A Characteristics and Criteria

Test Category A: Basic Biochar Utility Properties - Required for All Biochars			
Requirement	Criteria¹	Unit	Test Method
Moisture	Declaration	% of total mass, dry basis	ASTM D1762-84 (specify measurement date with respect to time from production)
Organic Carbon	Class 1: ≥60% Class 2: ≥30% and <60% Class 3: ≥10% and <30%	% of total mass, dry basis	C, H, N analysis by dry combustion (Dumas method), before (total C) and after (organic C) HCl addition
H:C _{org}	0.7 (Maximum)	Molar ratio	
Total Ash	Declaration	% of total mass, dry basis	ASTM D1762-84
Total Nitrogen	Declaration	% of total mass, dry basis	Dry combustion (Dumas method) and gas chromatography, following same procedure as for C, H, N analysis above, without HCl addition.
pH	Declaration	pH	pH analysis procedures as outlined in section 04.11 of US Composting Council and US Department of Agriculture (2001), following dilution and sample equilibration methods from Rajkovich et al. (2011) See Appendix 2.
Electrical Conductivity	Declaration	dS/m	EC analysis procedures as outlined in section 04.10 of US Composting Council and US Department of Agriculture (2001), following dilution and sample equilibration methods from Rajkovich et al. (2011) See Appendix 2.
Liming (if pH is above 7)	Declaration	% CaCO ₃	Rayment & Higginson (1992)
Particle size distribution	Declaration	% <420µm;	Progressive dry sieving with 4760µm, 2380µm and 420µm sieves, as outlined in ASTM D2862-10 Method for activated carbon.
		% 420-2,380 µm;	
		% 2,380-4,760 µm;	
		% >4,760 µm;	

¹ All values will be reported to one decimal place significant digit (0.1), unless otherwise indicated within the criteria for any reporting requirement. (e.g., if the analysis is 0.73, it can be reported as 0.7)

4.2 Test Category B - Toxicant Reporting

In addition to Test Category A thresholds and declarations, all biochar materials must meet the soil toxicity assessment thresholds as outlined in Table 2 below. Toxicants may be divided into two categories – those that may be present in the feedstocks used (metals and polychlorinated biphenyls) and those that may be produced by the thermochemical process used to make biochar (polycyclic aromatic hydrocarbons, and dioxins).

Biochar made from processed feedstocks may carry additional risks from the potential presence of toxicants in the feedstock and must meet the toxicant assessment testing frequency requirements of Section 6.

Biochar toxicity assessment reporting follows commonly identified soil toxicity and chemical content reporting requirements for soil amendments, composts and fertilizers. The threshold values in Table 2 are given as a range of values based on standards for soil amendments or fertilizers from a number of countries.² The Maximum Allowed Thresholds (MAT) indicate toxicant levels above which the material would not be considered acceptable. In order to meet the requirements of these *Biochar Guidelines*, reported toxicant levels must be below the MAT that has been established in the area of jurisdiction where biochar is produced and/or intended for use. If the area of jurisdiction where the biochar will be used has no threshold at all for a particular toxicant, the biochar must be below the highest maximum value established below for each specific toxicant. See Appendix 3, *Toxicant Assessment and Determination of Thresholds*, for more information.

Table 2: Test Category B Characteristics and Criteria

Test Category B: Biochar Toxicant Reporting - Required for All Feedstocks			
Requirement	Range of Maximum Allowed Thresholds		Test Method
Earthworm Avoidance Test	Pass/Fail		ISO 17512-1:2008 methodology and OECD methodology (1984a) as described by Van Zwieten et al. (2010), see Appendix 3
Germination Inhibition Assay	Pass/Fail		OECD methodology (1984b) 3 test species, as described by Van Zwieten et al. (2010), see Appendix 3
Polycyclic Aromatic Hydrocarbons (PAH)	6 – 20	mg /kg TM	Method following US Environmental Protection Agency (1996)
Dioxin/Furan (PCCD/F)	9	ng/kg I-TEQ	Method following US Environmental Protection Agency (2007)

² The following jurisdictions were used to construct the range of values: Australia, Canada, EU, UK, USA. These entities were chosen as standards because they all have a long history of regulations addressing these toxicants in soils and other substrates.

Table 2 (continued): Test Category B Characteristics and Criteria

Requirement	Range of Maximum Allowed Thresholds		Test Method
Polychlorinated Biphenyls	0.2 – 0.5	mg/kg I-TEQ	Method following US Environmental Protection Agency (1996)
Arsenic	12 – 100	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Cadmium	1.4 – 39	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Chromium	64 – 100	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Cobalt	100 – 150	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Copper	63 – 1500	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Lead	70 – 500	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Molybdenum	5 – 75	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Mercury	1 – 17	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Nickel	47 – 600	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Selenium	1 – 100	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Zinc	200 – 2800	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Boron	Declaration	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Chlorine	Declaration	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)
Sodium	Declaration	mg/kg dry wt	US Composting Council and US Department of Agriculture (2001)

4.3 Test Category C - Advanced Analysis and Soil Enhancement Properties

Test Category C is optional for all biochar materials. Producers may report on none, one, some, or all of the properties contained in the Test Category C set of advanced analysis and soil enhancement properties, using the prescribed test methods. Biochar advanced analysis characteristics include the volatile matter content, porosity, and surface area of biochars. Biochar soil enhancement properties identify plant nutrients contained in the biochar.

Biochars tested under Test Category C may report on any or all of the properties presented in Table 3 below:

Table 3: Test Category C Characteristics and Criteria

Test Category C: Biochar Advanced Analysis and Soil Enhancement Properties - Optional for All Biochars			
Requirement	Criteria	Unit	Test Method
Mineral N (ammonium and nitrate)	Declaration	mg/kg	2M KCl extraction, followed by spectrophotometry (Rayment and Higginson 1992)
Total Phosphorus & Potassium (P&K)*	Declaration	% of total mass, dry basis	Modified dry ashing followed by ICP (Enders and Lehmann 2012)
Available P	Declaration	mg/kg	2% formic acid followed by spectrophotometry (modified from Rajan et al 1992, Nutrient Cycl in Agroecosystems 32:291-302 and AOAC 2005, as used by Wang et al 2011)
Volatile Matter	Declaration	% of total mass, dry basis	ASTM D1762-84
Total Surface Area	Declaration	m2/g	ASTM D 6556-10 Standard Test Method for Carbon Black – Total and External Surface Area by Nitrogen Adsorption. See Appendix 2.
External Surface Area	Declaration	m2/g	
* Total K is sufficiently equivalent to available K for the purpose of this characterization			

5 Product Labeling and Documentation

Product labeling and documentation will be an important part of any biochar certification program. In order to qualify for certification, biochar producers and manufacturers must share information about the feedstock and final biochar material. Biochar test results and feedstock

origins must be uniformly labeled to communicate information that is important to end consumers and regulators. See Appendix 1 of this document for a sample label.

5.1 Labeling Instructions

To meet the requirements of these *Biochar Guidelines*, a label containing all of the required test results shall be attached, or provided in a web link, or otherwise included with all transactional documents, packaging, or other commercial documentation associated with the biochar material. The label shall be legible and placed in a fashion that is visible and clear on the biochar packaging or documentation.

5.2 Product Information Requirements

Included with the label, the manufacturer of the biochar shall make available to the purchaser information pertaining to:

- feedstock material composition and type, whether Processed or Unprocessed, including the identification of any diluents making up 10 percent or more of the total feedstock content;
- country of origin for the biochar feedstock;
- country where the biochar was produced; and
- country where the biochar will be sold for use.

5.3 Conformity and Record Keeping

Adequate documentation and reporting will be required by producers seeking to gain certification. The reporting of biochar feedstock and mandatory and optional test results are all necessary in order to provide assurance of end-product properties. Record keeping will be mandatory in order to establish proof of adequate sampling, testing, and results. Documentation of biochar feedstock (see Appendix 4 for guidelines on identifying feedstocks) and type (unprocessed or processed), production parameters (processing temperature and residence time), and test results should be kept for seven years. Individual biochar producers may wish to consult with a local attorney to determine whether recordkeeping for longer than seven years is appropriate, in light of state, regional, or provincial laws regarding product liability claims.

5.4 Chain of Custody

Chain of custody and product traceability will require an assurance that adequate care and transparency is being exercised to enable trace-back of final end-products from end users across the biochar market to manufacturers and feedstock suppliers. All entities in the biochar production and supply chain will be required to participate in record keeping to maintain quality assurance.

6 Testing Protocols

Biochar producers must follow the testing protocols described in this section, beginning with the selection of accredited laboratories using trained personnel to conduct the tests. Material changes in feedstocks and/or processing parameters will determine the timing of tests. In the case of Test Category B, the frequency of required testing will depend on the feedstocks used.

6.1 Laboratory Standards

Laboratory analysis of biochar shall be conducted by trained and accredited laboratory professionals following the appropriate procedures identified for each test. Please refer to Appendix 2 for further guidance on sampling procedures and sample processing and handling prior to analysis. Testing shall follow strict quality control requirements according to standardized laboratory procedures. Laboratory professionals are expected to be trained in the relevant field of analytical chemistry and operate in professional laboratories that have received general laboratory accreditation. Such accreditation should be provided by a relevant governing body or an international standards body like the ISO. The intent of such laboratory standards is to make certain that contributing laboratories will provide reliable and replicable results that will ensure that an appropriate standard of quality is met.

6.2 Timing and Frequency of Testing

Biochar testing and reporting of all Category A, B, and C Tests according to the *Biochar Guidelines* shall be performed:

- annually; or
 - after a material change in feedstock; or,
 - after a material change in thermochemical production parameters;
- whichever is more frequent.

Material changes in feedstock reflect shifts in feedstock type from one source of biomass to a distinctly different source of biomass. See Appendix 4 for more information on how to determine feedstock types that constitute a “material change” in type. In mixed feedstocks, whether processed or unprocessed, a 10% or greater shift in total feedstock composition shall constitute a material change in feedstock.

Material changes in production processes reflect increases or decreases in process temperature or residence time. A material change in thermochemical production parameters has occurred if process temperature (also known as Heat Treatment Temperature) changes by +/- 50°C, or if the thermochemical processing time (residence time) changes by more than 10%.


Testing of biochar materials should occur after thermochemical processing is complete and before final shipment. If the material is intended to be mixed with another material, testing of the biochar material must occur before mixing or blending with any other product.

6.3 Category B Test Requirements for Unprocessed Feedstocks

Category B Toxicant Assessment Tests shall follow the test frequency and reporting requirements given above, with the following exception for unprocessed feedstocks:

If the initial Category B test results for biochar made from an unprocessed feedstock are all within the Maximum Allowable Thresholds established by these *Biochar Guidelines*, then the Category B tests may be repeated every three years rather than annually, as long as the thermochemical production parameters and the feedstock composition all remain the same. Figure 1, below, is a set of two process flow charts that compares the initial testing requirements for all feedstock materials with the annual testing requirements, showing how the exception for unprocessed feedstocks is incorporated.

Figure 1: Process flow charts showing testing protocols for initial testing and annual testing of biochar materials.

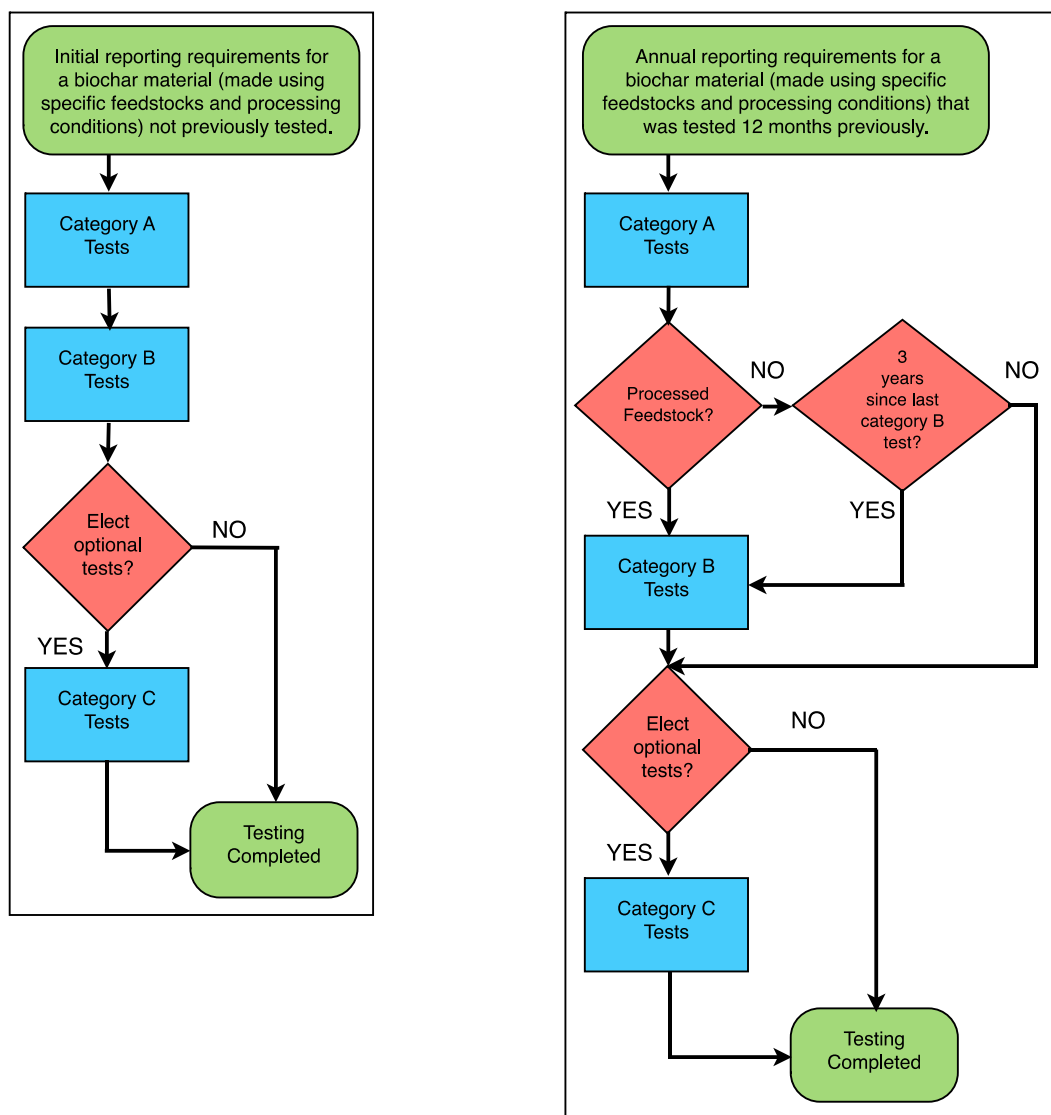

7 References

- Amlinger, F., Faroino, E., and Pollack, M. (2004) *EU Heavy Metals and Organic Compounds from Waste Used as Organic Fertilizers Final Report*. ENV.A.2./ETU/2001/0024 REF.NR.: TEND/AML/2001/07/20. (Accessed January 2012).
- AOAC (Association of Analytical Communities) International (2005) *AOAC Official Methods of Analysis. 18th Edition*. Latimer, G. (Ed.) www.eoma.aoc.org (accessed September 2011).
- ASTM International (2009) *ASTM –D6556-10 Standard Test Method for Carbon Black—Total and External Surface Area by Nitrogen Adsorption* <http://www.astm.org/Standards/D6556.htm> (accessed January 2012).
- ASTM International (2007) *ASTM D1762-84 (2007) Standard Test Method for Chemical Analysis of Wood Charcoal* <http://www.astm.org/Standards/D1762.htm> (accessed September 2011).
- ASTM International (2005) *ASTM D5158-98 (2005) Standard Test Method for Determination of Particle Size of Powdered Activated Carbon by Air Jet Sieving* <http://www.astm.org/Standards/D5158.htm> (accessed September 2011).
- Brinton, W.F. (2000) *Compost quality standards and guidelines*. Woods End Research Laboratory, prepared for New York State Association of Recyclers. <http://compost.css.cornell.edu/Brinton.pdf> (accessed September 2011).
- Bureau de normalisation du Québec (2005) *National Standard of Canada, Organic Soil Conditioners – Compost*. CAN/BNQ 0413-200 (2005) ISBN: 2-551-22659-7 http://www-es.criq.qc.ca/pls/owa_es/bnqw_norme.detail_norme?p_lang=en&p_id_norm=8184&p_code_menu=NORME (accessed September 2011).
- Canadian Council of Ministers of the Environment (CCME) (2002) *Canadian Soil Quality Guidelines for the Protection of Environmental and Human Health: Polychlorinated Dibenzo-p-Dioxins and Polychlorinated Dibenzofurans (PCDD/Fs)*. In: Canadian environmental quality guidelines, 1999, Canadian Council of Ministers of the Environment, Winnipeg Manitoba, Canada. ISBN 1-896997-34-1 <http://ceqg-rcqe.ccme.ca/> (accessed January 2012).
- Canadian Council of Ministers for the Environment (CCME) (2005) *Guidelines for Compost Quality*. PN 1340 Winnipeg Manitoba, Canada. ISBN 1-896997-60-0.
- Enders, A. and Lehmann, J. (2012) Comparison of wet digestion and dry ashing methods for total elemental analysis of biochar. *Communications in Soil Science and Plant Analysis*. 43:1042–1052.
- European Commission Agriculture and Rural Development (2010) *Biomass Potential* http://ec.europa.eu/agriculture/bioenergy/potential/index_en.htm (accessed September 2011).

- 1 European Commission COM(2006) *Directive Establishing a Framework for the Protection of Soil*
2 *and Amending Directive 2004/35/EC.*
3 http://ec.europa.eu/environment/soil/pdf/com_2006_0232_en.pdf (accessed September
4 2011).
- 5 International Biochar Initiative (2010) *IBI Guidelines for the Development and Testing of*
6 *Pyrolysis Plants to Produce Biochar* [http://www.biochar-](http://www.biochar-international.org/sites/default/files/IBI-Pyrolysis-Plant-Guidelines.pdf)
7 [international.org/sites/default/files/IBI-Pyrolysis-Plant-Guidelines.pdf](http://www.biochar-international.org/sites/default/files/IBI-Pyrolysis-Plant-Guidelines.pdf) (accessed
8 September 2011).
- 9 ISO 17512 - 1:2008 (2008) Soil quality - Avoidance test for determining the quality of soils and
10 effects of chemicals on behaviour - Part 1: Test with earthworms (*Eisenia fetida* and *Eisenia*
11 *andrei*) http://www.iso.org/iso/catalogue_detail.htm?csnumber=38402 (Accessed January
12 2012).
- 13 Li, D., Hockaday, W.C., Masiello, C.A. and Alvarez, P.J.J. (2011) Earthworm avoidance of
14 biochar can be mitigated by wetting. *Soil Biology & Biochemistry*. 43:1732-1737.
- 15 Milne, T.A.; Brennan, A.H.; Glenn, B.H. *Sourcebook of Methods of Analysis for Biomass*
16 *Conversion and Biomass Conversion Processes*. SERI/SP-220-3548. Golden, CO: Solar
17 Energy Research Institute, February 1990.
- 18 National Institute of Health, National Cancer Institute, *Dictionary of Cancer Terms*,
19 <http://www.cancer.gov/dictionary?cdrid=687391> (Accessed February 2012)
- 20 OECD Organisation for Economic Co-operation and Development (1984a) Earthworm acute
21 toxicity tests no. 207. In *Guideline for testing of chemicals*. ISBN 9789264070042
22 <http://browse.oecdbookshop.org/oecd/pdfs/free/9720701e.pdf>. (Accessed January 2012).
- 23 OECD Organisation for Economic Co-operation and Development (1984b) Terrestrial Plants,
24 Growth Test no. 208. In *Guideline for Testing of Chemicals*.
25 <http://www.oecd.org/dataoecd/18/0/1948285.pdf>. (Accessed January 2012).
- 26 Rajan, S.S.S., Brown, M.W., Boyes, M.K., and Upsdell, M.P. (1992) Extractable phosphorus to
27 predict agronomic effectiveness of ground and unground phosphate rocks. *Nutrient*
28 *Cycling in Agroecosystems*. 32(3):291-302.
- 29 Rajkovich, S., Enders, A., Hanley, K., Hyland, C., Zimmerman, A.R., and Lehmann, J. (2011)
30 Corn growth and nitrogen nutrition after additions of biochars with varying properties to
31 a temperate soil. *Biol Fertil Soils*. DOI 10.1007/s00374-011-0624-7. Published Online.
- 32 Rayment, G.E. and Higginson, F.R. (1992). *Australian Laboratory Handbook of Soil and Water*
33 *Chemical Methods*. Reed International Books, Australia/ Inkata Press, Port Melbourne.
- 34 Rayment, G.E., and Lyons, D.J. (2011) *Soil Chemical Methods – Australasia*. CSIRO Publishing,
35 Collingwood, Victoria, Australia.
- 36 Stockholm Convention. *What are POPs?*
37 <http://chm.pops.int/Convention/ThePOPs/tabid/673/Default.aspx> (Accessed March 2012).

- 1 US Composting Council and US Department of Agriculture (2001) *Test methods for the*
2 *examination of composting and compost. (TMECC)* Thompson W.H. (ed.)
3 <http://compostingcouncil.org/tmecc/>. (Accessed January 2012).
- 4 US Environmental Protection Agency (1996) *METHOD 8275A Semivolatile organic compounds*
5 *(PAHs AND PCBs) in soils/sludges and solid wastes using thermal extraction/gas*
6 *chromatography/mass spectrometry (TE/GC/MS).*
7 <http://www.epa.gov/osw/hazard/testmethods/sw846/pdfs/8275a.pdf> (accessed
8 September 2011).
- 9 US Environmental Protection Agency (1999) *Background report on fertilizer use, contaminants*
10 *and regulations.* Prepared by BATELLE, Columbus OH. National Program Chemicals
11 Division; Office of Pollution Prevention and Toxics, Washington D.C.
12 <http://www.epa.gov/oppt/pubs/fertilizer.pdf>, via
13 <http://www.epa.gov/agriculture/tfer.html>. (Accessed February 2012).
- 14 US Environmental Protection Agency (2007) *EPA METHOD 8290A Polychlorinated Dibenzo-P-*
15 *Dioxins (PCDDs) and polychlorinated dibenzofurans (PCDFs) by high resolution gas*
16 *chromatography/high resolution mass spectrometry (HRGC/HRMS).*
17 <http://www.epa.gov/osw/hazard/testmethods/sw846/pdfs/8290a.pdf> (Accessed
18 September 2011).
- 19 US Geological Service. *Polynuclear Aromatic Hydrocarbons (PAHs)/Polycyclic Aromatic*
20 *Hydrocarbons (PAHs)* <http://toxics.usgs.gov/definitions/pah.html> (Accessed March
21 2012).
- 22 VanZwieten, L., Kimber, S., Morris, S., Chan, K.Y., Downie, A., Rust, J., Joseph, S., and Cowie,
23 A. (2010) Effects of biochar from slow pyrolysis of papermill waste on agronomic
24 performance and soil fertility. *Plant and Soil* 327:235-246. DOI 10.1007/s11104-009-
25 0050-x.
- 26 Wang, T., Camps Arbestain, M., Hedley, M., and Bishop, P. (2012) Predicting phosphorus
27 bioavailability from high-ash biochars. *Plant and Soil*. DOI 10.1007/s11104-012-1131-9.
28 Published Online.

Appendix 1 – Sample Biochar Label

Figure A1.1 below is an example of adequate product labeling with the necessary product information as specified in these *Biochar Guidelines*.

Producers who wish to report on the properties of biochar contained in a blended product must also report the percentage of biochar as an ingredient in that product and make it clear that the information reported on the biochar label applies to the biochar portion only.

Figure A1.1 Sample Label for a Biochar Product

GOOD GROW BIOCHAR	
MATERIAL TYPE	Biochar made from declared feedstock
COUNTRY OF ORIGIN	Australia
COUNTRY OF USE	Australia
FEEDSTOCK COUNTRY OF ORIGIN	Australia
FEEDSTOCK TYPE	Processed Feedstock
FEEDSTOCK COMPOSITION DECLARATION	poultry manure - 83%, wood chip bedding - 17%
BIOCHAR BASIC UTILITY PROPERTIES	
Moisture (at time of analysis)	20% - DECLARATION
Organic Carbon	42% - CLASS 2 BIOCHAR
H:C _{org}	0.6 - PASS
Total Ash	40% - DECLARATION
Total N	5.4% - DECLARATION
pH	7.5 - DECLARATION
Electrical Conductivity	7.3 dS/m - DECLARATION
Liming	23% CaCO ₃
Particle Size Distribution	5% <420µm;
	35% 420-2,380 µm;
	45% 2,380-4,760 µm;
	15% >4,760 µm
BIOCHAR ADVANCED ANALYSIS AND SOIL ENHANCEMENT PROPERTIES	
Mineral N (ammonium and nitrate)	21 mg/kg - DECLARATION
Total P&K	3.1% P, 4.4%K - DECLARATION
Available P	16 mg/kg - DECLARATION
Volatile Matter	6.8% - DECLARATION
Total Surface Area	790 m ² /g- DECLARATION
External Surface Area	160 m ² /g- DECLARATION

TOXICANT ASSESSMENT	
Earthworm Avoidance Test	PASS
Germination Inhibition Assay	PASS
Polycyclic Aromatic Hydrocarbons (PAH)	6 mg /kg TM - PASS
Dioxin/Furan (PCDD/F)	0.02 ng/kg I-TEQ - PASS
Polychlorinated Biphenyls (PCB)	0.2 mg/kg I-TEQ - PASS
Arsenic	10 mg/kg - PASS
Cadmium	1.2 mg/kg - PASS
Chromium	60 mg/kg - PASS
Cobalt	14 mg/kg - PASS
Copper	143 mg/kg - PASS
Lead	125 mg/kg - PASS
Molybdenum	5 mg/kg - PASS
Mercury	0.5 mg/kg - PASS
Nickel	25 mg/kg - PASS
Selenium	10 mg/kg - PASS
Zinc	320 mg/kg - PASS
Boron	20 mg/kg- DECLARATION
Chlorine	90 mg/kg- DECLARATION
Sodium	140 mg/kg- DECLARATION
Please see attached MSDS documentation for appropriate shipping, handling, and storage procedures.	

1

2

3

4

Appendix 2 – Recommended General Sample Analysis Procedures and Protocols for Specific Tests

Biochar sampling

Strict adherence to standardized biochar sampling procedures is critical to ensure reliable, representative, and replicable test results. Following accepted compost analysis practices, the Test Methods for the Examination of Composting and Composts (TMECC) (US Composting Council and US Department of Agriculture (2001)) has been identified as an effective general sampling procedure to comply with the *Biochar Guidelines*. The TMECC documents provide detailed descriptions of sampling procedures for piles of unsorted, potentially heterogeneous material, which result in homogeneous, representative samples to be used in subsequent chemical analysis (Section 02.01 Field Sampling of Compost Materials in US Composting Council and US Department of Agriculture (2001)). Adhering to TMECC sampling guidance will ensure consistency in analytical approach, since subsequent physicochemical analyses within the *Biochar Guidelines* document recommend the use of TMECC methodologies.

Sample handling and processing

Since sample handling and processing is analysis-methodology-dependent, appropriate procedures should be selected based upon the chemical tests that will be conducted. Sample processing can vary depending upon the physicochemical analyses to be conducted; sample preparation methods followed should be specifically intended for the selected physicochemical tests to be conducted. For example, sample preparation methods can include grinding and sieving or oven-drying for analysis, to provide the dry weight measure indicated in Table 3 of the biochar test categories. General sample preparation procedures can be found in TMECC Section 02.02 Laboratory Sample Preparation in US Composting Council and US Department of Agriculture (2001). Caution should be exercised however, since the methodologies recommended therein are designed for compost, and not for biochar. Comments within the TMECC document (US Composting Council and US Department of Agriculture (2001)) indicate that sample heating can occur while grinding, which can result in a change in sample qualities and characteristics. To avoid this, it is recommended that samples to be ground and sieved to a smaller size range (e.g. 2mm) be hand-ground in a mortar and pestle, to reduce the risk of heating, sparking, or ignition (following sample grinding methods for pH and EC assessment noted in Rajkovich et al, 2011).

Combined approach to analyzing pH and EC

Generic pH and EC analysis procedures have been drawn from the TMECC methodologies (US Composting Council and US Department of Agriculture (2001)). These procedures for the use of

control and reference pH samples and electrode probes have been adapted for use with biochar, as follows: where the TMECC methodology recommends a 1:5 (v:v or w:w)³ solution of compost:deionized water, a 1:20 (w:v)⁴ solution of biochar:deionized water should be used for biochar pH and EC analysis, following Rajkovich et al (2011). Similarly, additional time should be allotted for solution equilibration after the combination of deionized water and biochar. Following Rajkovich et al (2011), 1.5 hours should be provided for the shaking and equilibration of biochar-deionized-water solutions prior to pH and EC analysis. Upon completion of the shaking and equilibration phase, pH and EC analysis may be conducted on the same samples, rather than making separate replicates for pH and EC. To complete the pH and EC analysis follow methodologies 04.10 and 04.11 of the TMECC methodology (US Composting Council and US Department of Agriculture (2001)).

Earthworm Avoidance and Germination Inhibition Assay

The Earthworm Avoidance and Germination Inhibition Assay analyses follow procedures outlined by Van Zwieten et al 2010. The recommended approach for biochar analysis is to follow Van Zwieten et al's methods, as they are drawn from the initial 1984 OECD and ISO 17512 - 1:2008 methodologies, and to report earthworm behavior as it relates to the avoidance of biochar-soil, and seedling germination as it relates to the failure to germinate in biochar-soil. Lettuce (*Lactuca sativa* L.) is the most widely recommended species to use in germination assessments, due to its sensitivity. Other species that can be used are found within the OECD (1984b) methodology. The primary approach to the earthworm avoidance test is drawn from ISO 17512 – 1:2008, with instructions on soil matrix blending from the OECD (1984a) methodology. Further augmentations of Van Zwieten et al's approach should follow Li et al (2011) to ensure that adequate wetting of soil and biochar-soil blends is achieved for the duration of the Earthworm Avoidance test. Results should be reported as a "fail" to reflect a statistically significant preference of the worms to avoid biochar-blended soils, or a failure of seedling germination and growth in biochar-blended soils, thus rejecting the null-hypothesis that there is no difference between biochar-soil blends and soil within the test. Results can be reported as a "pass" where there is no difference of worm preference or germination and seedling growth success between biochar-soil blends and soil, or where biochar-soil blends are preferred; both conditions are considered to pass these tests. The purpose of the analyses is to determine whether adding biochar to soil has an effect on worm behaviour and seed

³ v:v – volume:volume denotes a ratio based on equivalent units of volume measurement in a dilution or blend (e.g. a 1:5 v:v biochar:water blend indicates the need to blend 1 ml of biochar with 5 ml of water)
w:w – weight:weight denotes a ratio based on equivalent units of weight measurement in a dilution or blend (e.g. a 1:5 w:w biochar:soil blend indicates the need to blend 1 g of biochar with 5 g of soil)

⁴ w:v – weight:volume denotes a blend or dilution ratio expressed as grams of solid per milliliter of liquid. (e.g. a 1:20 w:v biochar:water blend indicates the need to blend 1 mg of biochar with 20 ml of water)

germination. It is assumed that a negative effect indicates the presence of undesirable compounds in the biochar material.

Analysis of Surface Area

The analysis of surface area will follow the methodologies presented in ASTM D6556-10: Standard Test Method for Carbon Black – Total and External Surface Area by Nitrogen Adsorption. Although carbon blacks can be made at much higher temperatures than biochar, the identified Brunauer, Emmett and Teller (BET) procedure will be effective for analyzing biochar surface area, with the following additional steps:

1. The relevant measure is the B.E.T. nitrogen surface area ("BET NSA").
2. The Vacuum Degassing method should be used (section 8.5) in preference to the Flow Degassing (8.4).
3. Section 8.5.3 Degassing temperature should not exceed 250 °C to avoid further thermochemical alteration of the sample, as some biochars are made at temperatures as low as 300 °C. The times necessary to degas may greatly exceed the ½ hour mentioned in this section of the analysis; up to 48 hours can be used to conduct the analysis, however this time must be reported along with the results. The actual time needed will depend on the instrument tolerance level, which is dictated by the manufacturer.
4. As indicated in section 9.6, a minimum of five evenly-spaced data points can be presented between 0.05 and 0.5 p/p₀. Two additional data points, at 0.05 and 0.075 p/p₀ should also be presented in the results.
5. The mass of sample on which the measurement is based should be determined after the surface area measurement has been completed.
6. The instrument should be calibrated periodically with a reference standard supplied by the manufacturer to make sure it is in good working order according the manufacturer's specifications.

Final units for surface area analysis should be reported in square meters per gram (m²/g).

References

- ASTM International (2009) *ASTM –D6556-10 Standard Test Method for Carbon Black—Total and External Surface Area by Nitrogen Adsorption*
<http://www.astm.org/Standards/D6556.htm> (accessed January 2012).
- ISO 17512 - 1:2008 (2008) *Soil quality - Avoidance test for determining the quality of soils and effects of chemicals on behaviour - Part 1: Test with earthworms (Eisenia fetida and Eisenia andrei)* http://www.iso.org/iso/catalogue_detail.htm?csnumber=38402 (Accessed January 2012).

- 1 Li, D., Hockaday, W.C., Masiello, C.A., and Alvarez, P.J.J. (2011) Earthworm avoidance of
2 biochar can be mitigated by wetting. *Soil Biology and Biochemistry* 43(8):1732–1737.
- 3 OECD Organisation for Economic Co-operation and Development (1984a) Earthworm acute
4 toxicity tests no. 207. In *Guideline for Testing of Chemicals*. ISBN 9789264070042
5 <http://browse.oecdbookshop.org/oecd/pdfs/free/9720701e.pdf>. (Accessed January 2012).
- 6 OECD Organisation for Economic Co-operation and Development (1984b) Terrestrial Plants,
7 Growth Test no. 208. In *Guideline for Testing of Chemicals*.
8 <http://www.oecd.org/dataoecd/18/0/1948285.pdf>. (Accessed January 2012).
- 9 Rajkovich, S., Enders, A., Hanley, K., Hyland, C., Zimmerman, A.R., and Lehmann, J. (2011)
10 Corn growth and nitrogen nutrition after additions of biochars with varying properties to
11 a temperate soil. *Biol Fertil Soils* 48(3):271-284.
- 12 US Composting Council and US Department of Agriculture (2001) *Test methods for the*
13 *examination of composting and compost. (TMECC)* Thompson W.H. (ed.)
14 <http://compostingcouncil.org/tmecc/>. (Accessed January 2012).
- 15 Van Zwieten, L., Kimber, S., Morris, S., Chan, K.Y., Downie, A., Rust, J., Joseph, S., and Cowie,
16 A. (2010) Effects of biochar from slow pyrolysis of papermill waste on agronomic
17 performance and soil fertility. *Plant Soil* 327:235-246. DOI 10.1007/s11104-009-0050-x.

Appendix 3 – Toxicant Assessment and Determination of Thresholds

The following table indicates the maximum allowed toxicant thresholds for some jurisdictions, including the European Union (EU), United Kingdom (UK), Australia, Canada, and the United States (US) that were used to help develop reporting levels for the *Biochar Guidelines*. These entities were chosen as resources for toxicant standards due to their history of regulations addressing these toxicants in soils and other substrates, and their development of similar soil quality standards (e.g. land-application of biosolids, wood ash, and/or compost). Toxicant ranges for reporting to the IBI are **not** indicated within this appendix, and are instead indicated within Table 2 as part of Test Category B. The below table is intended to provide a better understanding of how the IBI developed the maximum threshold ranges indicated in Table 2 through a survey of international regulations.

Table A3.1 – International toxicant regulation resources used for determining IBI range of maximum allowed thresholds.

Toxicant	International Regulatory Maximum Toxicant Thresholds	
Polycyclic Aromatic Hydrocarbons (PAH)	6(A), 20(B)	mg EPA PAH/kg TM
Dioxin/Furan (PCDD/F)	9 (F)	ng/kg TEQ (dry wt)
Polychlorinated Biphenyls (PCBs)	0.2(A), 0.5(C)	mg/kg TM or TEQ
Arsenic	100(B), 12(C), 41(D), 75(E)	mg/kg (dry wt)
Cadmium	1.4(A), 20(B), 1.4(C), 39(D), 20(E)	mg/kg (dry wt)
Chromium	93(A), 100(B), 64(C)	mg/kg (dry wt)
Cobalt	100(B), 150(E)	mg/kg (dry wt)
Copper	143(A), 1000(B), 63(C), 1500(D)	mg/kg (dry wt)
Lead	121(A), 300(B), 70(C), 300(D), 500(E)	mg/kg (dry wt)
Molybdenum	5(C), 75(D), 20(E)	mg/kg (dry wt)
Mercury	1(A), Methyl mercury 10(B), Inorganic mercury 15(B), 6.6(C), 17(D), 5(E)	mg/kg (dry wt)
Nickel	47(A), 600(B), 50(C), 420(D), 180(E)	mg/kg (dry wt)
Selenium	1(C), 100(D), 14(E)	mg/kg (dry wt)
Zinc	416(A), 200(C), 2800(D), 1850(E)	mg/kg (dry wt)

- 1 (A) Amlinger F., Favoino E. and Pollack M., (2004) Heavy metals and organic compounds from
2 wastes used as organic fertilisers. Final Report July 2004 REF. Nr. TEND/AML/2001/07/20
3 ENV.A.2./ETU/2001/0024 <http://www.bvsde.paho.org/bvsacd/cd43/used.pdf> (accessed January
4 2012). Data has been taken from Table S1. Regulatory data from EU countries (Austria, Belgium,
5 Germany, Denmark, Spain, France, Finland, Greece, Italy, Ireland, Luxembourg, Netherlands,
6 Portugal, Sweden, and United Kingdom) was averaged to produce the reported values. Toxicant
7 values are reported as mg/kg of dry mass samples. NB: Individual nations within the EU will
8 have different regulatory expectations than the average values reported herein; appropriate
9 regulatory values should be followed, rather than regional averages.
- 10 (B) Australia National Environment Protection NEPC 1999 Assessment of Site Contamination Measure
11 Schedule B(1) Guideline on the Investigation Levels for Soil and Groundwater. See Schedule B1,
12 specifically, for relevant toxicant information. www.ephc.gov.au/contam (accessed January
13 2012).
- 14 (C) Canadian Council of Ministers of the Environment (CCME) 2001; 2006 Soil Quality Guidelines for
15 the Protection of Environmental and Human Health (first published 1999, updated 2001, 2002,
16 2003, 2004, 2005, 2006 & 2007). <http://st-ts.ccme.ca> (accessed January 2012).
- 17 (D) United States Environmental Protection Agency (US EPA) 1994 A Plain English Guide to the EPA
18 Part 503 Biosolids Rule US EPA 40 CFT Part 503 US EPA, Office of Wastewater Management,
19 Washington DC. EPA/832/R-93/003.
20 http://water.epa.gov/scitech/wastetech/biosolids/503pe_index.cfm (accessed January 2012).
- 21 (E) Bureau de Normalisation du Quebec 2005 National Standard of Canada Organic Soil Conditioners
22 – Composts (as a source of threshold levels, Maximum Content for Type B compost was used)
23 [http://www-
24 es.criq.qc.ca/pls/owa_es/bnqw_norme.detail_norme?p_lang=en&p_id_norm=8184&p_code_men
25 u=NORME](http://www-es.criq.qc.ca/pls/owa_es/bnqw_norme.detail_norme?p_lang=en&p_id_norm=8184&p_code_menu=NORME) (accessed January 2012).
- 26 (F) Alberta Environment 2002 Standards and Guidelines for the Use of Wood Ash as a Liming
27 Material for Agricultural Soils. Science and Standards Branch, Edmonton, Alberta. ISBN: 0-7785-
28 2281-4 (online edition). The Alberta Guideline sets the threshold value for PCDD/F in wood ash at
29 27 ng/kg based on an assumed cumulative application of 45 tonnes/hectare over 100 years.
30 Biochar may be applied in larger total amounts. Under the assumption that the maximum
31 cumulative application of biochar over a 100-year period is 135 tonnes/hectare⁵, a linear
32 extrapolation yields a threshold value for PCDD/F concentration of 9 ng/kg, I-TEQ.
33
34

⁵ Glaser, B., Lehmann, J., and Zech, W. (2002) Ameliorating physical and chemical properties of highly weathered soils in the tropics with charcoal - a review. *Biology and Fertility of Soils* 35(4):219-230.

Appendix 4 – Determining a “Material Change” in Feedstock

This Appendix addresses the need to identify feedstock types for purposes of determining a “material change” in feedstock types under Section 6.2 – *Timing and Frequency of Testing*. Section 6.2 requires that biochar properties and characteristics according to the specification guidelines shall be assessed and reported after every “material change” in feedstock.

Unprocessed Feedstocks

Table A4.1 is a list of distinct unprocessed feedstock types used to make biochar. Changes between these feedstock types will constitute a “material change” in feedstock. Types are based on biomass composition as listed in the Phyllis Biomass Composition Database (see reference).

Any change in feedstock from one listed type in Table A4.1 to another shall constitute a “material change” in feedstock.

Feedstocks not listed in this table may be used to make biochar if they meet the other feedstock requirements outlined in these guidelines. However, any change between a feedstock listed in Table A4.1 and a feedstock not listed will constitute a “material change” in feedstock and require a new round of testing.

If an unprocessed feedstock not listed in Table A4.1 is changed to another unprocessed feedstock not listed in Table A4.1, then a “material change” in feedstock shall be based on the species of plant material used for the feedstock, so that a change in species constitutes a “material change” in feedstock.

Table A4.1 – Unprocessed Feedstock Types

Unprocessed Feedstock Types for determining "material change" in feedstock
Rice hulls & straw
Non-maize cereal straws & switchgrass
Maize cobs & stover
Sugar cane bagasse & trash
Softwoods (conifers)
Hardwoods (angiosperms)
Bamboo
Miscanthus

Mixed Feedstocks

When a mix of unprocessed feedstocks is used, a change of 10% or more in the total feedstock composition shall constitute a “material change” in feedstock. The magnitude of the change in the feedstock shall be calculated by adding up the decreases in percentages for each individual feedstock type composing the mixed feedstock. The following is an illustrative example:

Rosie’s Biochar is typically made of:

- 35% spruce wood chips,
- 25% aspen wood chips,
- 15% wheat straw,
- 15% assorted leaves and
- 10% corn stover.

This past year, due to a change in spruce availability, her feedstock changed to:

- 25% spruce wood chips,
- 35% aspen wood chips,
- 15% wheat straw,
- 15% assorted leaves and
- 10% corn stover.

Because a 10% total change in feedstock has occurred, Rosie must re-test her biochar.

If Rosie’s biochar had instead changed from her typical blend in the following way, she would still need to re-test her biochar because a 10% total change in feedstock has also occurred:

- 38% spruce wood chips,
- 20% aspen wood chips,
- 20% wheat straw,
- 17% assorted leaves and
- 5% corn stover.

Processed Feedstocks

Table A4.2 is a list of feedstocks sourced from processed biomass. Any change from one processed feedstock to another will constitute a “material change” in feedstock, e.g.:

1. a change from sheep manure to pig manure;
2. a change from sludge/waste provided by Facility A to that by Facility B; or
3. a significant change in the process parameters (e.g., a change in process chemistry for paper sludge, or a change from dairy manure to pig manure in an anaerobic digester process).

Processed feedstocks not listed in this table may be used to make biochar if they meet the other feedstock requirements outlined in these guidelines.

When a mix of different processed feedstocks is used, or where the processed feedstock consists of a mix of components, a change of 10% or more in the total feedstock composition shall constitute a "material change" in feedstock. Please see the above example of Rosie's biochar using unprocessed feedstocks for a better understanding of how to assess total feedstock composition changes of at least 10%.

Table A4.2 – Processed Feedstock Types

Processed Feedstock Types for determining "material change" in feedstock
Cattle manure
Pig manure
Chicken manure
Sheep manure
Horse manure
Paper mill sludge
Sewage sludge
Distillers grain
Anaerobic digester sludge
Biomass fraction of MSW
Food industry waste

References

Phyllis, database for biomass and waste, Version: 4.13, Energy Research Centre of the Netherlands (ECN), <http://www.ecn.nl/phyllis> (accessed 03 January 2012).

Appendix 5 – The Use of H:C_{org} to Indicate C Stability

The molar H:C_{org} ratio is recommended to distinguish biochar from other thermochemically altered organic matter for several reasons:

1. H:C ratios change substantially with thermochemical treatment (Keiluweit et al., 2010);
2. O:C ratios have been shown to correlate well with stability of biochars (Spokas, 2010);
3. H:C and O:C ratios are closely related (for low-ash biochars <50% ash and <80% volatiles (ash-free basis));
4. H is determined directly in most laboratories, whereas O is calculated by subtraction.

The modification of using the organic C values rather than total C for this ratio is motivated by the presence of inorganic carbonates in some high-ash biochars. These inorganic carbonates do not form aromatic groups distinctive of biochar materials.

The molar H:C_{org} ratio is a material property that is correlated with the degree of thermochemical alteration that produces fused aromatic ring structures in the material. The presence of these structures is an intrinsic measure of the stability of the material.

The upper H:C_{org} limit of 0.7 is used to distinguish biochars from biomass that has not been thermochemically altered and from other materials that have been only somewhat thermochemically altered. We use the term “thermochemically converted” to refer to thermochemically altered materials that have an H:C_{org} below 0.7. These materials have a greater proportion of fused aromatic ring structures. Other thermochemically processed materials that have an H:C_{org} value greater than 0.7 may be thermochemically “altered” but they are not considered to be thermochemically “converted”.

Figure A5.1 below shows relationships between processing temperature and H:C_{org} molar ratio for a number of thermochemically altered materials, as compared to unprocessed biomass.

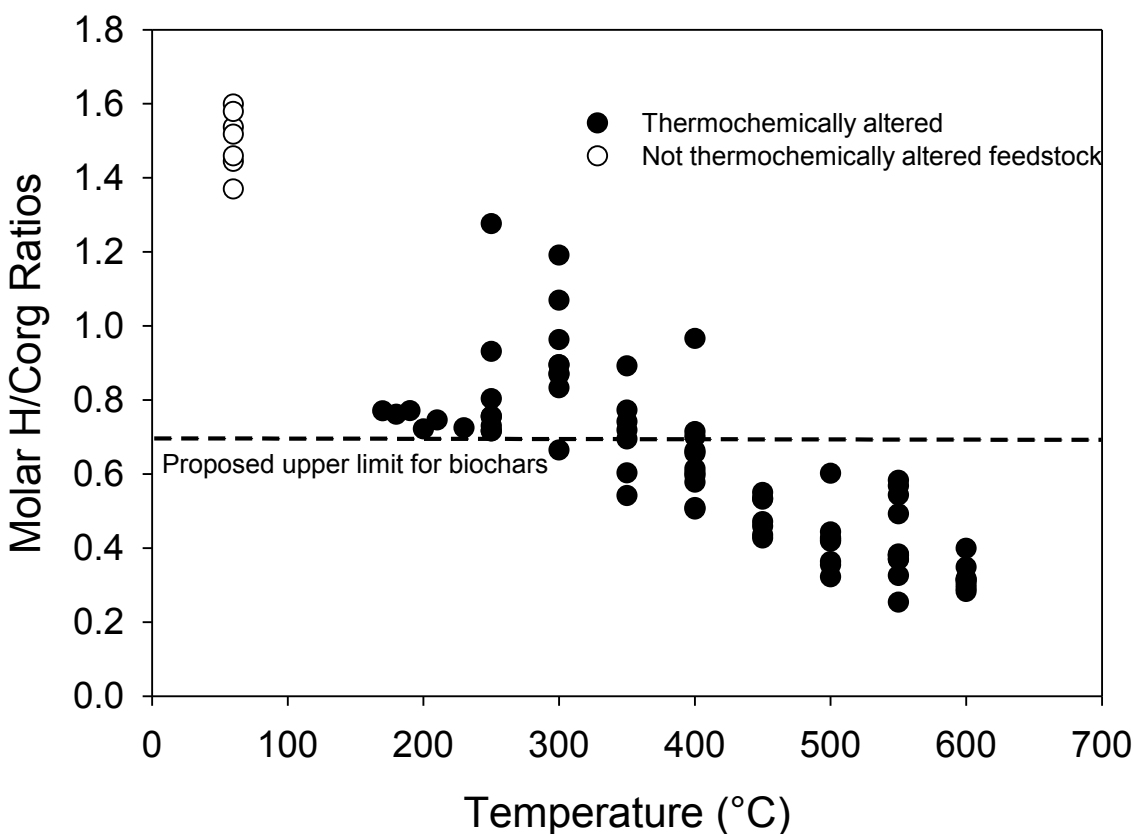


Figure A5.1: Relationship between molar H:C_{org} ratios and temperature of thermochemically altered organic matter in comparison to untreated biomass. Dashed line is the upper limit of 0.7. Data points below the 0.7 line are thermochemically altered materials that are considered to be thermochemically “converted” (data from Sevilla and Fuertes, 2009ab; Calvelo Pereira et al, 2011; Enders et al., 2012).

References

- Enders A., Hanley K., Whitman T., Joseph S. and Lehmann J. Characterization of biochars to evaluate recalcitrance and agronomic performance. *Bioresource Technology* (BITE-D-11-04505). Published online.
- Keiluweit M., Nico P.S., Johnson M.G. and Kleber M. (2010) Dynamic molecular structure of plant-derived black carbon (biochar). *Environmental Science and Technology* 44:1247-1253.
- Sevilla M. and Fuertes A.B. (2009a) Chemical and structural properties of carbonaceous products obtained by hydrothermal carbonization of saccharides. *Chemistry - A European Journal* 15:4195-4203.

- 1 Sevilla M. and Fuertes A.B. (2009b) The production of carbon materials by hydrothermal
2 carbonization of cellulose. *Carbon* 47:2281–2289.
- 3 Spokas K.A. (2010) Review of the stability of biochar in soils: predictability of O:C molar ratios.
4 *Carbon Management* 1:289-303.
- 5 Calvelo Pereira, R., Kaal, J., Camps Arbestain, M., Pardo Lorenzo, R., Aitkenhead, W., Hedley,
6 M., , F., Hindmarsh, J., - , J.A. (2011) Contribution to characterisation
7 of biochar to estimate the labile fraction of carbon. *Organic Geochemistry* 42:1331–
8 1342.

Appendix 6 – Glossary

List of Acronyms and Abbreviations

AOAC – Association of Analytical Communities

ASTM – American Society for Testing and Materials

BNQ – Bureau de Normalisation du Quebec (a member of the National Standards System of Canada, involved in developing product and process standards for Canadians)

C – Carbon

CaCO₃ – Calcium Carbonate

C_{org} – Organic Carbon

CCME – Canadian Council of Ministers of the Environment

CSIRO – Commonwealth Scientific and Industrial Research Organisation, Australia

dS – decisiemens

dS/m – decisiemens per meter

dry wt – dry weight

EC – Electrical Conductivity

EPA – Environmental Protection Agency, United States

EU – European Union

g – gram

GHG – Greenhouse Gas

H – Hydrogen

HCl – hydrochloric acid

HMIS – Hazardous Materials Identification System

IBI – International Biochar Initiative

ICP – Inductively Coupled Plasma

IEEE – Institute of Electrical and Electronics Engineers

- 1 ISO – International Organization for Standardization
- 2 I-TEQ – International Toxicity Equivalent
- 3 K – Potassium
- 4 KCl – potassium chloride
- 5 kg – kilogram
- 6 m – meter
- 7 mg – milligram
- 8 M – molar
- 9 MAT – Maximum Allowable Threshold
- 10 MSDS – Material Safety Data Sheet
- 11 MSW – Municipal Solid Waste
- 12 NEPC – National Environment Protection Council, Australia
- 13 ng – nanogram
- 14 OECD – Organisation for Economic Co-operation and Development
- 15 OMS – Office of Mobile Sources, division of US EPA
- 16 P – Phosphorus
- 17 PAH – Polycyclic Aromatic Hydrocarbon
- 18 PCB – Polychlorinated Biphenyl
- 19 PCDD – Polychlorinated Dibenzodioxin (Dioxin)
- 20 PCDF – Polychlorinated Dibenzofuran (Furan)
- 21 PCDD/F – Dioxins/Furans
- 22 POPs – Persistent Organic Pollutants
- 23 S – Siemens
- 24 S/m – Siemens per meter
- 25 SA – Surface Area
- 26 TM – Total Mass

1 TMECC – Test Methods for the Examining of Composting and Compost, from US Composting
2 Council and USDA

3 USDA – United States Department of Agriculture

4 USGS – United States Geological Service

5 µg – microgram

6

7 **Definition of Terms**

8 *Note: Terms and definitions have been adapted from the references given. Terms and*
9 *definitions created specifically for this document are referenced as "IBI".*

10 Ash: The inorganic matter, or mineral residue of total solids, that remains when a sample is
11 combusted in the presence of excess air. (US Compost Council and US Department of
12 Agriculture, 2001)

13 Biochar: A solid material obtained from thermochemical conversion of biomass in an oxygen-
14 limited environment. (IBI, 2012)

15 Biochar Characteristics: For the purposes of these guidelines, biochar characteristics are those
16 physical or chemical properties of biochar that affect the following uses for biochar: 1) biochar
17 that is added to soils with the intention to improve soil functions; and 2) biochar that is
18 produced in order to reduce emissions from biomass that would otherwise naturally degrade to
19 GHG, by converting a portion of that biomass into a stable carbon fraction that has carbon
20 sequestration value. (IBI, 2012)

21 Biological Material: Material derived from, or produced by, living or recently living organisms.
22 This material can be "unprocessed" or "processed". Unprocessed biological material is living
23 material, or recently living material from the plant kingdom (or other non-animal taxa such as
24 fungi or algae) that may have been mechanically resized (such as wood chips), but has not
25 been processed in an animal's body or gone through an anthropogenic chemical modification.
26 Processed biological material is recently living material that has been chemically modified by
27 anthropogenic or biological processes (e.g., paper sludge, manure). All animal products,
28 including bones, offal, food-waste containing animal products, and animal manures are
29 considered to be processed biological material. (IBI, 2012)

30 Biomass: The biodegradable fraction of products, waste and residues of biological origin from
31 agriculture (including vegetal and animal substances), forestry, and related industries including
32 fisheries and aquaculture, as well as the biodegradable fraction of industrial and municipal
33 waste (including municipal solid waste). (European Commission Agriculture and Rural
34 Development, 2010)

1 Contaminant: An undesirable material in a biochar material or biochar feedstock that
2 compromises the quality or usefulness of the biochar or through its presence or concentration
3 causes an adverse effect on the natural environment or impairs human use of the environment.
4 (Adapted from Canadian Council of Ministers of the Environment, 2005). Contaminants include
5 fossil fuels and fossil-fuel-derived chemical compounds, glass, and metal objects. (IBI, 2012)

6 Diluent/Dilutant: Inorganic material that is deliberately mixed or inadvertently comingled with
7 biomass feedstock prior to processing. These materials will not carbonize in an equivalent
8 fashion to the biomass. These materials include soils and common constituents of natural soils,
9 such as clays and gravel that may be gathered with biomass or intermixed through prior use of
10 the feedstock biomass. Diluents/dilutants may be found in a diverse range of feedstocks, such
11 as agricultural residues, manures, and municipal solid wastes. (IBI, 2012)

12 Dioxin: The term "dioxin" is commonly used to refer to a family of chemicals that share
13 chemical structures and characteristics. These compounds include polychlorinated dibenzo
14 dioxins (PCDDs) and polychlorinated dibenzo furans (PCDFs), which are unwanted by-products
15 of industrial and natural processes, usually involving combustion. Dioxins are listed as Persistent
16 Organic Pollutants by the Stockholm Convention. (IBI, 2012)

17 Feedstock: The material undergoing the thermochemical process to create biochar. Feedstock
18 material for biochar consists of biological material, but may also contain diluents. (IBI, 2012)

19 Fossil-Fuel-Derived Chemical Compounds: This category of contaminant includes any compound
20 of a synthetic nature, created from hydrocarbons, including, but not limited to plastics, solvents,
21 paints, resins, and tars. Because of the blending of wastes and use of synthetic materials to
22 bind and label other materials (e.g. plastic flagging tape in forestry residues), fossil-fuel-derived
23 chemical compounds have become commonplace in multiple waste streams, and are often
24 difficult to separate from feedstocks prior to processing. These contaminants can contain highly
25 toxic chemicals like polychlorinated biphenyls (PCBs) that may act as bioaccumulators and affect
26 the resulting quality of biochar. (IBI, 2012)

27 Hazardous Materials or Wastes: Potential environmental pollutants that, when concentrated,
28 can be a source of regulatory concern for any use or application that may influence human or
29 environmental health and wellbeing. (Adapted from US Composting Council and US Department
30 of Agriculture, 2001)

31 Heat Treatment Temperature: The temperature at which a feedstock material is processed
32 during thermochemical conversion in a biochar production process. (IBI, 2012)

33 Municipal Waste/Municipal Solid Waste (MSW): solid non-hazardous refuse that originates from
34 residential, industrial, commercial, institutional, demolition, land clearing, or construction
35 sources (Canadian Council of Ministers of the Environment 2005). Municipal solid waste includes
36 durable goods, non-durable goods, containers and packaging, food wastes and yard trimmings,
37 and miscellaneous inorganic wastes. (US Environmental Protection Agency, 2011)

1 Organic Carbon: Biologically degradable carbon-containing compounds found in the organic
2 fraction of biochar feedstocks. Biochar feedstocks can contain such compounds as sugars,
3 starches, proteins, fats, cellulose, and lignocellulose, which are thermochemically degradable.
4 Other organic carbon forms can include petroleum and petroleum by-products such as plastics
5 and contaminated oils, which are, for the purposes of this document, included within the
6 definition of contaminants, but may also be thermochemically degraded. The organic carbon
7 fraction does not include inorganic carbonate concretions such as calcium and magnesium
8 carbonates. (Adapted from US Composting Council and US Department of Agriculture, 2001)

9 Persistent Organic Pollutants (POPs): POPs are organic chemical substances, that is, they are
10 carbon-based. They possess a particular combination of physical and chemical properties such
11 that, once released into the environment, remain intact for exceptionally long periods of time
12 (many years); become widely distributed throughout the environment as a result of natural
13 processes involving soil, water and, most notably, air; accumulate in the fatty tissue of living
14 organisms including humans, and are found at higher concentrations at higher levels in the food
15 chain; and are toxic to both humans and wildlife. (Stockholm Convention, 2012)

16 Polychlorinated biphenyls (PCBs): PCBs are a group of organic compounds used in the
17 manufacture of plastics, as lubricants, and dielectric fluids in transformers, in protective coating
18 for wood, metal and concrete, and in adhesives and wire coating. PCBs have been banned in
19 most countries and are no longer manufactured, but sources remain in the environment in the
20 form of products and waste. The Stockholm Convention lists PCBs as POPs. (IBI, 2012)

21 Polycyclic aromatic hydrocarbons (PAHs): PAHs refer to a family of compounds built from two or
22 more benzene rings. Sources of PAHs include fossil fuels and incomplete combustion of organic
23 matter, in auto engines, incinerators, forest fires, charcoal grilling, or other biomass burning.
24 PAHs are usually found as a mixture containing two or more of these compounds, such as soot.
25 Out of hundreds of different PAH compounds, only a few are considered to be highly toxic and
26 of regulatory concern. (Adapted from USGS, 2012)

27 Processed Feedstock: Biomass that has gone through chemical processing (for example, paper
28 pulp sludge) or biological processing (for example, digestion, such as manures and sludge from
29 waste effluent treatment) beyond simple mechanical processing to modify physical properties.
30 Because animals may bioaccumulate toxicants in their tissues, all animal parts and products are
31 considered to be Processed Feedstocks for purposes of these guidelines. Any biomass material
32 that may have been grown on soils contaminated with heavy metals or other toxicants will also
33 be considered a Processed Feedstock for purposes of these guidelines. (IBI, 2012)

34 Producer and/or Manufacturer: The party or parties who process feedstock materials into
35 biochar, test the biochar properties, and acquire appropriate labeling. (IBI, 2012)

36 Residence Time: The time a feedstock is held within a consistent temperature range in a given
37 thermochemical process. (IBI, 2012)

1 Soil Functions: Soil functions include: "(i) biomass production, including in agriculture and
2 forestry; (ii) storing, filtering and transforming nutrients, substances and water; (iii) hosting the
3 biodiversity pool, such as habitats, species and genes; (iv) acting as a platform for human
4 activities; (v) source of raw materials; (vi) acting as carbon pool; and (vii) storing geological
5 and archeological heritage." (European Soil Framework Directive COM, 2006, p. 232)

6 Toxicants: Chemical or physical agents that, depending on dose, can produce adverse effects in
7 biological organisms (adapted from Trush 2008). These chemicals may be essential for some
8 plants and animals at low levels, or in a specific oxidation state, but can be toxic at higher
9 concentrations or in a different oxidation state. Toxicants may be naturally present in soils or
10 artificially produced by human activity. (Adapted from US EPA, 1999)

11 Unprocessed Feedstock: Biomass from the plant kingdom (or other non-animal taxa such as
12 fungi and algae), grown in a clean, uncontaminated environment, that may have gone through
13 mechanical processing to change its physical properties (e.g., particle size), but has not gone
14 through chemical processing or treatment, or biological processing (e.g., digestion). (IBI, 2012)

15 Volatile Matter: Those products, exclusive of moisture, given off by a material as a gas or vapor,
16 determined by definite prescribed methods that may vary according to the nature of the
17 material. (Milne et al, 1990)

18

Appendix 7 – Creative Commons License



Creative Commons Legal Code

Attribution-NonCommercial-NoDerivs 3.0 Unported

CREATIVE COMMONS CORPORATION IS NOT A LAW FIRM AND DOES NOT PROVIDE LEGAL SERVICES. DISTRIBUTION OF THIS LICENSE DOES NOT CREATE AN ATTORNEY-CLIENT RELATIONSHIP. CREATIVE COMMONS PROVIDES THIS INFORMATION ON AN "AS-IS" BASIS. CREATIVE COMMONS MAKES NO WARRANTIES REGARDING THE INFORMATION PROVIDED, AND DISCLAIMS LIABILITY FOR DAMAGES RESULTING FROM ITS USE.

License

THE WORK (AS DEFINED BELOW) IS PROVIDED UNDER THE TERMS OF THIS CREATIVE COMMONS PUBLIC LICENSE ("CCPL" OR "LICENSE"). THE WORK IS PROTECTED BY COPYRIGHT AND/OR OTHER APPLICABLE LAW. ANY USE OF THE WORK OTHER THAN AS AUTHORIZED UNDER THIS LICENSE OR COPYRIGHT LAW IS PROHIBITED.

BY EXERCISING ANY RIGHTS TO THE WORK PROVIDED HERE, YOU ACCEPT AND AGREE TO BE BOUND BY THE TERMS OF THIS LICENSE. TO THE EXTENT THIS LICENSE MAY BE CONSIDERED TO BE A CONTRACT, THE LICENSOR GRANTS YOU THE RIGHTS CONTAINED HERE IN CONSIDERATION OF YOUR ACCEPTANCE OF SUCH TERMS AND CONDITIONS.

1. Definitions

a. "Adaptation" means a work based upon the Work, or upon the Work and other pre-existing works, such as a translation, adaptation, derivative work, arrangement of music or other alterations of a literary or artistic work, or phonogram or performance and includes cinematographic adaptations or any other form in which the Work may be recast, transformed, or adapted including in any form recognizably derived from the original, except that a work that constitutes a Collection will not be considered an Adaptation for the purpose of this License. For the avoidance of doubt, where the Work is a musical work, performance or phonogram, the synchronization of the Work in timed- relation with a moving image ("synching") will be considered an Adaptation for the purpose of this License.

b. "Collection" means a collection of literary or artistic works, such as encyclopedias and anthologies, or performances, phonograms or broadcasts, or other works or subject matter other than works listed in Section 1(f) below, which, by reason of the selection and arrangement of their contents, constitute intellectual creations, in which the Work is included in its entirety in unmodified form along with one or more other contributions, each constituting separate and independent works in themselves, which together are assembled into a collective whole. A work that constitutes a Collection will not be considered an Adaptation (as defined above) for the purposes of this License.

- 1 c. "Distribute" means to make available to the public the original and copies of the Work
2 through sale or other transfer of ownership.
- 3 d. "Licensor" means the individual, individuals, entity or entities that offer(s) the Work under the
4 terms of this License.
- 5 e. "Original Author" means, in the case of a literary or artistic work, the individual, individuals,
6 entity or entities who created the Work or if no individual or entity can be identified, the
7 publisher; and in addition (i) in the case of a performance the actors, singers, musicians,
8 dancers, and other persons who act, sing, deliver, declaim, play in, interpret or
9 otherwise perform literary or artistic works or expressions of folklore; (ii) in the case of a
10 phonogram the producer being the person or legal entity who first fixes the sounds of a
11 performance or other sounds; and, (iii) in the case of broadcasts, the organization that
12 transmits the broadcast.
- 13 f. "Work" means the literary and/or artistic work offered under the terms of this License
14 including without limitation any production in the literary, scientific and artistic domain,
15 whatever may be the mode or form of its expression including digital form, such as a
16 book, pamphlet and other writing; a lecture, address, sermon or other work of the same
17 nature; a dramatic or dramatico-musical work; a choreographic work or entertainment in
18 dumb show; a musical composition with or without words; a cinematographic work to
19 which are assimilated works expressed by a process analogous to cinematography; a
20 work of drawing, painting, architecture, sculpture, engraving or lithography; a
21 photographic work to which are assimilated works expressed by a process analogous to
22 photography; a work of applied art; an illustration, map, plan, sketch or three-
23 dimensional work relative to geography, topography, architecture or science; a
24 performance; a broadcast; a phonogram; a compilation of data to the extent it is
25 protected as a copyrightable work; or a work performed by a variety or circus performer
26 to the extent it is not otherwise considered a literary or artistic work.
- 27 g. "You" means an individual or entity exercising rights under this License who has not
28 previously violated the terms of this License with respect to the Work, or who has
29 received express permission from the Licensor to exercise rights under this License
30 despite a previous violation.
- 31 h. "Publicly Perform" means to perform public recitations of the Work and to communicate to
32 the public those public recitations, by any means or process, including by wire or
33 wireless means or public digital performances; to make available to the public Works in
34 such a way that members of the public may access these Works from a place and at a
35 place individually chosen by them; to perform the Work to the public by any means or
36 process and the communication to the public of the performances of the Work, including
37 by public digital performance; to broadcast and rebroadcast the Work by any means
38 including signs, sounds or images.
- 39 i. "Reproduce" means to make copies of the Work by any means including without limitation by
40 sound or visual recordings and the right of fixation and reproducing fixations of the
41 Work, including storage of a protected performance or phonogram in digital form or
42 other electronic medium.

2. Fair Dealing Rights. Nothing in this License is intended to reduce, limit, or restrict any uses free from copyright or rights arising from limitations or exceptions that are provided for in connection with the copyright protection under copyright law or other applicable laws.

3. License Grant. Subject to the terms and conditions of this License, Licensor hereby grants You a worldwide, royalty-free, non-exclusive, perpetual (for the duration of the applicable copyright) license to exercise the rights in the Work as stated below:

a. to Reproduce the Work, to incorporate the Work into one or more Collections, and to Reproduce the Work as incorporated in the Collections; and,

b. to Distribute and Publicly Perform the Work including as incorporated in Collections.

The above rights may be exercised in all media and formats whether now known or hereafter devised. The above rights include the right to make such modifications as are technically necessary to exercise the rights in other media and formats, but otherwise you have no rights to make Adaptations. Subject to 8(f), all rights not expressly granted by Licensor are hereby reserved, including but not limited to the rights set forth in Section 4(d).

4. Restrictions. The license granted in Section 3 above is expressly made subject to and limited by the following restrictions:

b. You may Distribute or Publicly Perform the Work only under the terms of this License. You must include a copy of, or the Uniform Resource Identifier (URI) for, this License with every copy of the Work You Distribute or Publicly Perform. You may not offer or impose any terms on the Work that restrict the terms of this License or the ability of the recipient of the Work to exercise the rights granted to that recipient under the terms of the License. You may not sublicense the Work. You must keep intact all notices that refer to this License and to the disclaimer of warranties with every copy of the Work You Distribute or Publicly Perform. When You Distribute or Publicly Perform the Work, You may not impose any effective technological measures on the Work that restrict the ability of a recipient of the Work from You to exercise the rights granted to that recipient under the terms of the License. This Section 4(a) applies to the Work as incorporated in a Collection, but this does not require the Collection apart from the Work itself to be made subject to the terms of this License. If You create a Collection, upon notice from any Licensor You must, to the extent practicable, remove from the Collection any credit as required by Section 4(c), as requested.

c. You may not exercise any of the rights granted to You in Section 3 above in any manner that is primarily intended for or directed toward commercial advantage or private monetary compensation. The exchange of the Work for other copyrighted works by means of digital file-sharing or otherwise shall not be considered to be intended for or directed toward commercial advantage or private monetary compensation, provided there is no payment of any monetary compensation in connection with the exchange of copyrighted works.

d. If You Distribute, or Publicly Perform the Work or Collections, You must, unless a request has been made pursuant to Section 4(a), keep intact all copyright notices for the Work and provide, reasonable to the medium or means You are utilizing: (i) the name of the

Original Author (or pseudonym, if applicable) if supplied, and/or if the Original Author and/or Licensor designate another party or parties (e.g., a sponsor institute, publishing entity, journal) for attribution ("Attribution Parties") in Licensor's copyright notice, terms of service or by other reasonable means, the name of such party or parties; (ii) the title of the Work if supplied; (iii) to the extent reasonably practicable, the URI, if any, that Licensor specifies to be associated with the Work, unless such URI does not refer to the copyright notice or licensing information for the Work. The credit required by this Section 4(c) may be implemented in any reasonable manner; provided, however, that in the case of a Collection, at a minimum such credit will appear, if a credit for all contributing authors of Collection appears, then as part of these credits and in a manner at least as prominent as the credits for the other contributing authors. For the avoidance of doubt, You may only use the credit required by this Section for the purpose of attribution in the manner set out above and, by exercising Your rights under this License, You may not implicitly or explicitly assert or imply any connection with, sponsorship or endorsement by the Original Author, Licensor and/or Attribution Parties, as appropriate, of You or Your use of the Work, without the separate, express prior written permission of the Original Author, Licensor and/or Attribution Parties.

a. For the avoidance of doubt:

i. Non-waivable Compulsory License Schemes. In those jurisdictions in which the right to collect royalties through any statutory or compulsory licensing scheme cannot be waived, the Licensor reserves the exclusive right to collect such royalties for any exercise by You of the rights granted under this License;

ii. Waivable Compulsory License Schemes. In those jurisdictions in which the right to collect royalties through any statutory or compulsory licensing scheme can be waived, the Licensor reserves the exclusive right to collect such royalties for any exercise by You of the rights granted under this License if Your exercise of such rights is for a purpose or use which is otherwise than noncommercial as permitted under Section 4(b) and otherwise waives the right to collect royalties through any statutory or compulsory licensing scheme; and,

iii. Voluntary License Schemes. The Licensor reserves the right to collect royalties, whether individually or, in the event that the Licensor is a member of a collecting society that administers voluntary licensing schemes, via that society, from any exercise by You of the rights granted under this License that is for a purpose or use which is otherwise than noncommercial as permitted under Section 4(b).

b. Except as otherwise agreed in writing by the Licensor or as may be otherwise permitted by applicable law, if You Reproduce, Distribute or Publicly Perform the Work either by itself or as part of any Collections, You must not distort, mutilate, modify or take other derogatory action in relation to the Work which would be prejudicial to the Original Author's honor or reputation.

5. Representations, Warranties and Disclaimer

UNLESS OTHERWISE MUTUALLY AGREED BY THE PARTIES IN WRITING, LICENSOR OFFERS THE WORK AS-IS AND MAKES NO REPRESENTATIONS OR WARRANTIES OF ANY KIND

1 CONCERNING THE WORK, EXPRESS, IMPLIED, STATUTORY OR OTHERWISE, INCLUDING,
2 WITHOUT LIMITATION, WARRANTIES OF TITLE, MERCHANTABILITY, FITNESS FOR A
3 PARTICULAR PURPOSE, NONINFRINGEMENT, OR THE ABSENCE OF LATENT OR OTHER
4 DEFECTS, ACCURACY, OR THE PRESENCE OF ABSENCE OF ERRORS, WHETHER OR NOT
5 DISCOVERABLE. SOME JURISDICTIONS DO NOT ALLOW THE EXCLUSION OF IMPLIED
6 WARRANTIES, SO SUCH EXCLUSION MAY NOT APPLY TO YOU.

7 6. Limitation on Liability. EXCEPT TO THE EXTENT REQUIRED BY APPLICABLE LAW, IN NO
8 EVENT WILL LICENSOR BE LIABLE TO YOU ON ANY LEGAL THEORY FOR ANY SPECIAL,
9 INCIDENTAL, CONSEQUENTIAL, PUNITIVE OR EXEMPLARY DAMAGES ARISING OUT OF THIS
10 LICENSE OR THE USE OF THE WORK, EVEN IF LICENSOR HAS BEEN ADVISED OF THE
11 POSSIBILITY OF SUCH DAMAGES.

12 7. Termination

13 a. This License and the rights granted hereunder will terminate automatically upon any breach
14 by You of the terms of this License. Individuals or entities who have received Collections
15 from You under this License, however, will not have their licenses terminated provided
16 such individuals or entities remain in full compliance with those licenses. Sections 1, 2,
17 5, 6, 7, and 8 will survive any termination of this License.

18 b. Subject to the above terms and conditions, the license granted here is perpetual (for the
19 duration of the applicable copyright in the Work). Notwithstanding the above, Licensor
20 reserves the right to release the Work under different license terms or to stop
21 distributing the Work at any time; provided, however that any such election will not
22 serve to withdraw this License (or any other license that has been, or is required to be,
23 granted under the terms of this License), and this License will continue in full force and
24 effect unless terminated as stated above.

25 8. Miscellaneous

26 a. Each time You Distribute or Publicly Perform the Work or a Collection, the Licensor offers to
27 the recipient a license to the Work on the same terms and conditions as the license granted
28 to You under this License.

29 b. If any provision of this License is invalid or unenforceable under applicable law, it shall not
30 affect the validity or enforceability of the remainder of the terms of this License, and
31 without further action by the parties to this agreement, such provision shall be reformed to
32 the minimum extent necessary to make such provision valid and enforceable.

33 c. No term or provision of this License shall be deemed waived and no breach consented to
34 unless such waiver or consent shall be in writing and signed by the party to be charged with
35 such waiver or consent.

36 d. This License constitutes the entire agreement between the parties with respect to the Work
37 licensed here. There are no understandings, agreements or representations with respect to
38 the Work not specified here. Licensor shall not be bound by any additional provisions that
39 may appear in any communication from You. This License may not be modified without the
40 mutual written agreement of the Licensor and You.

e. The rights granted under, and the subject matter referenced, in this License were drafted utilizing the terminology of the Berne Convention for the Protection of Literary and Artistic Works (as amended on September 28, 1979), the Rome Convention of 1961, the WIPO Copyright Treaty of 1996, the WIPO Performances and Phonograms Treaty of 1996 and the Universal Copyright Convention (as revised on July 24, 1971). These rights and subject matter take effect in the relevant jurisdiction in which the License terms are sought to be enforced according to the corresponding provisions of the implementation of those treaty provisions in the applicable national law. If the standard suite of rights granted under applicable copyright law includes additional rights not granted under this License, such additional rights are deemed to be included in the License; this License is not intended to restrict the license of any rights under applicable law.

Creative Commons Notice

Creative Commons is not a party to this License, and makes no warranty whatsoever in connection with the Work. Creative Commons will not be liable to You or any party on any legal theory for any damages whatsoever, including without limitation any general, special, incidental or consequential damages arising in connection to this license. Notwithstanding the foregoing two (2) sentences, if Creative Commons has expressly identified itself as the Licensor hereunder, it shall have all rights and obligations of Licensor.

Except for the limited purpose of indicating to the public that the Work is licensed under the CCPL, Creative Commons does not authorize the use by either party of the trademark "Creative Commons" or any related trademark or logo of Creative Commons without the prior written consent of Creative Commons. Any permitted use will be in compliance with Creative Commons' then-current trademark usage guidelines, as may be published on its website or otherwise made available upon request from time to time. For the avoidance of doubt, this trademark restriction does not form part of this License.

Creative Commons may be contacted at <http://creativecommons.org>.